

CATALYTIC ACTION OF NITRIC ACID ON THE HYDROLYSIS
OF ETS-40 ETHYL SILICATEIryna Lutsyuk^{1, ✉}, Yaroslav Vakhula¹, Iryna Tupis¹, Iryna Iliuchok¹<https://doi.org/10.23939/chcht15.04.475>

Abstract. The effect of concentrated nitric acid on the hydrolysis rate of ETS-40 ethyl silicate has been studied. The duration and maximum temperature of ethyl silicate hydrolysis at different temperatures of the components have been determined. The formation of silica particles in the xerogel structure is shown. The influence of the ETS-40 hydrolysis on the particles size and concentration has been examined. The structure of the xerogel and the composition of the formed particles have been investigated using scanning electron microscopy (SEM) and energy dispersion analysis (EDX).

Keywords: ETS-40 ethyl silicate, hydrolysis, xerogel, silica particles.

1. Introduction

In recent years the scientific progress in all fields necessitates the development of new materials with high operating properties and functionalities. This, in turn, requires the improvement of existing and the development of new technologies.

One of the advanced technologies for obtaining silicate materials (ceramic powders of submicron sizes, thin-layer glass coatings, functional glass fibers and films) is sol-gel technology [1-3]. This technology involves the preparation of the sol of the required composition, a gradual increase in its viscosity with the formation of a homogeneous gel. Further use of the gel and corresponding modes of its processing are determined by the purpose of the final product. True or colloidal solution is used to obtain thin-layer glass coatings on metal, ceramics, *etc.* [4, 5]. The dried gel allows to obtain powders of the required size, which, in turn, serve as a basis for the synthesis of ceramic products for technical purposes, composite medical materials, *etc.* [6, 7].

The advantages of sol-gel technology are a high homogeneity degree of the solution, the ability to control the particle size and chemical composition of the powder,

an avoidance of the grinding stage and, most importantly, a significant reduction in energy costs. Materials for carrying out the sol-gel process are water-soluble salts or alkoxides of metals.

In the case of obtaining materials which contain silicon(IV) oxide, usually TEOS (ethyl ester of orthosilicic acid $\text{Si}(\text{OC}_2\text{H}_5)_4$) or ETS of different composition (ethyl silicate, which is a mixture of orthosilicic acid esters derivatives with different molecular weight and molecular structure, ETS-32, ETS-40) are used. To obtain silicon-containing colloidal solutions, these products are not used in pure form. To transfer the prepared solutions from the sol to the gel, it is necessary to carry out their preliminary hydrolysis.

Analysis of numerous publications, in particular [8], on the production of organo-inorganic composite materials shows that tetraethoxysilane solutions in organic solvents (acetone, isopropyl alcohol, *etc.*) cause the greatest interest as the binders.

Commercial ethyl silicates, which are produced today, differ in the concentration of SiO_2 and the amount of tetraethoxysilane introduced with the products of complete or partial polymerization/condensation. Therefore, to obtain high-quality solvent-free sol-gel composite materials, an individual approach to the hydrolysis of ethyl silicates is required.

Among the main factors that determine the processes of hydrolytic polycondensation and gelation of ethyl silicate gels are: pH of the medium, concentration and nature of the catalyst, as well as the ratio of ethyl silicate : water. In the alkaline medium the reaction rate directly depends on the alkali concentration; in the acid medium it depends on the catalyst concentration and type, which, in turn, determines the production of a certain gel structure [9].

The aim of this work is to study the kinetics of the hydrolysis reaction of ETS-40 in the medium of nitric acid and the selection of optimal conditions for obtaining the technological sol.

2. Experimental

The initial materials were ETS-40 (standard) and concentrated nitric acid of PA grade. The components

Lviv Polytechnic National University
12, Bandery St., Lviv, 79013, Ukraine¹

✉ KhTS.dept@lpnu.ua

© Lutsyuk I., Vakhula Y., Tupis I., Iliuchok I., 2021

were kept in a refrigerator at 275–278 K for 12 h. Each component was weighed on an analytical weight with an accuracy of ± 0.0001 g.

The ethyl silicate hydrolysates were prepared in a thermally insulated closed beaker (volume 100 ml) under constant stirring using a laboratory magnetic stirrer. The hydrolysate temperature was recorded every 30 s with an accuracy of ± 0.1 K using a stationary thermometer installed in the beaker. Temperature measurements were stopped when the hydrolysate reached ambient temperature.

The morphology and structure of the gels fracture were studied using a ZEISS EVO 40XVP scanning electron microscope with an INCA Energy 350 detector. Surface images were obtained by recording secondary electrons by scanning with an electron beam (20 keV).

The chemical composition of the particles was investigated by energy dispersion analysis (EDX).

The pH value of the sols was determined using an ionomer I-160MI.

Taking into account the influence of various factors on the ethyl silicate hydrolysis, as well as the mechanism and rate of polycondensation, the following conditions were adopted to obtain the sol.

Hydrolysis of ethyl silicate should be carried out in the presence of an acid catalyst at a ratio of $n\text{H}_2\text{O}/\text{C}_2\text{H}_5\text{O} = 3$ according to the reaction (1):



Concentrated nitric acid was used as an acid hydrolysis catalyst; its amount was 0.2–0.8 wt % relative to the total content of ethyl silicate and water, which provides pH of 1–2. Multicomponent gels are obtained on the basis of hydrolysate with the addition of nitrates of the corresponding metals. In this regard, nitric acid was used as a catalyst to ensure chemical anionic homogeneity. The pH value of the hydrolysate was 1.5–1.6 and did not change during the whole process.

The calculated amount of concentrated nitric acid was previously added to the distilled water, and the

resulting solution was evenly added dropwise to ETS-40. Since ethyl silicate and water are mutually insoluble, and the hydrolysis reaction occurs only at the interface of the liquids, it is necessary to constantly stir the solution.

3. Results and Discussion

To determine the effect of temperature of the initial materials on hydrolysis process the components at room temperature (NP series) and the components cooled to 275–278 K (NO series) were used.

When 0.2 % of HNO_3 (NP series) is introduced into the system, the maximum temperature of 313 K is reached after 170 min (Fig. 1a). A further increase in the amount of acid catalyst to 0.8 % leads to a significant intensification of the hydrolysis reaction, which is confirmed by further studies. The maximum hydrolysis reaction temperature increases, namely: 0.4 % of HNO_3 leads to the increase in temperature to 320 K (74 min), 0.6 % – to 322 K (44 min) and 0.8 % – to 326 K (32 min). It should be noted that due to hydrolysis, the system with 0.8 % of HNO_3 converts into a viscous state. Therefore, a further increase in the amount of acid catalyst for the hydrolysis of ethyl silicate was considered impractical.

It is known [3] that the increase in the hydrolysis time leads to the free rapid evaporation of volatile products, which ensures the purity of the gel, and in combination with the increase in hydrolysate temperature contributes to the aggregation of sol particles. Therefore, in order to obtain homogeneous solutions, it was decided to use components cooled to 275–278 K (NO series).

One can see (Fig. 1b), that the cooling of components provides the increase in time necessary to achieve the maximum hydrolysis temperature by 2–3 times and reduce it by an average of 7–10 K. The parameters of the hydrolysis process are given in Table 1.

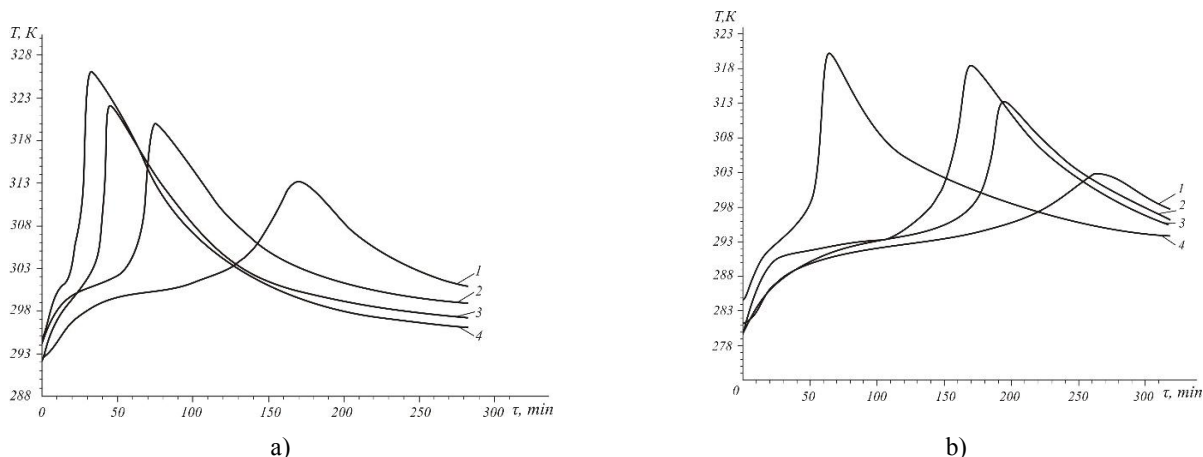


Fig. 1. Hydrolysis kinetics of ETS-40 of NP series (a) and NO series (b) with different amount of concentrated HNO_3 , wt %: 0.2 (1); 0.4 (2); 0.6 (3) and 0.8 (4)

Table 1

Parameters of ETC-40 hydrolysis

Symbol	HNO ₃ amount, wt %	Temperature of the initial compounds, K	Maximal temperature of hydrolysis, K	Time for achieving maximal temperature, min
NP1	0.2	291–293	313	170
NP2	0.4		320	74
NP3	0.6		322	44
NP4	0.8		326	32
NO1	0.2	275–278	303	260
NO2	0.4		313	195
NO3	0.6		318	170
NO4	0.8		320	65

Additional information on the kinetics of ETS condensation according to the selected modes is given by the results of SEM analysis. When examining the fresh fracture surface of all xerogels one can see that amorphous particles of various sizes of indeterminate shape are observed against the background of the matrix gel.

EDX analysis was used to determine the content of elements in the formed particles. Thus, it was established (Fig. 2, spectrum 1) that the composition of the specified particle includes silicon and oxygen (Table in Fig. 2). The obtained data allow to assert that each particle consists of silica – SiO₂.

To establish the effect of the initial components temperature on the main parameters of silica particles, we carried out a comparative analysis of xerogel samples obtained by components hydrolysis at room temperature (NP series samples) and cooled to 275–278 K (NO series samples).

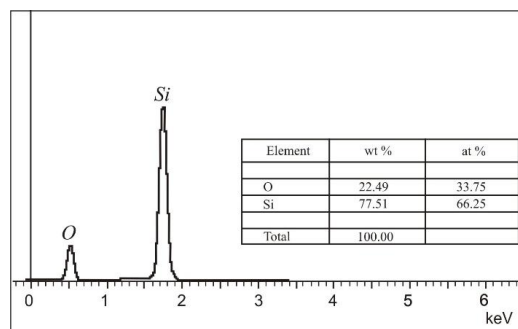


Fig. 2. Elemental analysis of the particles in the xerogel structure

Studies have shown that changes in the concentration of nitric acid have a significant effect on both the size of individual particles and their number in individual areas. The number of particles was counted visually at the places of their maximum allocation on the area of 100 μm².

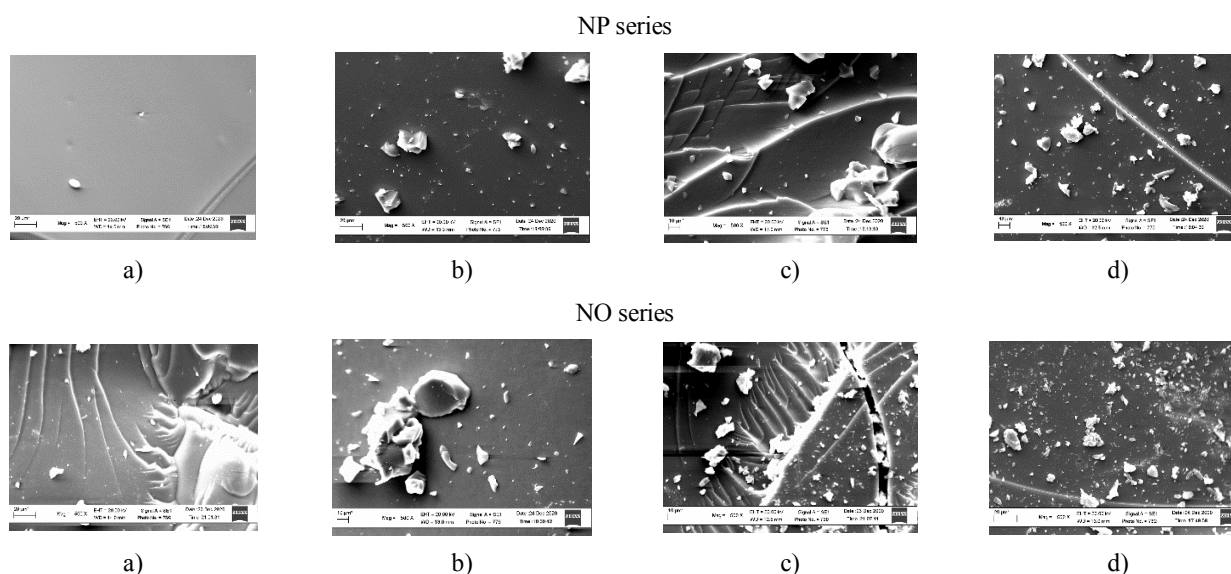


Fig. 3. Structure of fresh fracture of xerogel with HNO₃ amount of (wt %): 0.2 (a); 0.4 (b); 0.6 (c) and 0.8 (d)

Table 2

Symbol	Amount of HNO ₃ , wt%	Number of particles, units	Particles size, μm
NP1	0.2	1	10
NP2	0.4	2–4	0.1–5
NP3	0.6	5–7	1–20
NP4	0.8	6–7	0.5–15
NO1	0.2	4–5	1–15
NO2	0.4	6–7	1–10
NO3	0.6	6–9	0.5–8
NO4	0.8	11–12	0.5–5

With HNO₃ amount of 0.2 wt % (Fig. 3a) allocation of siliceous particles is practically not observed (only some of them are visible). The increase in HNO₃ amount to 0.4 and 0.6 wt % causes the appearance of a greater number of particles. Their size is mainly 2–5 μm, although some of them reach 20 μm. Their concentration increases (Table 2).

The number of particles increases sharply in the presence of 0.8 wt % of HNO₃ (Fig. 3d). Their size ranges from 0.5 to 15 μm and their number in some areas is 6–7 units.

The introduction of even 0.2 wt % of HNO₃ into the cooled solution provides the formation of SiO₂ particles with the size of 1–15 μm; their number is 4–5 units (Fig. 3b).

Further increase in the HNO₃ amount leads to a sharp increase in the number of particles, and at 0.8 wt % their number is almost twice (11–12 units) as high as for similar solution of the NP series. The size of most particles decreases to 0.5–2 μm.

4. Conclusions

The amount of acid catalyst was found to be an important and effective factor influencing the hydrolysis rate of ETS-40 ethyl silicate. Thus, when the amount increases from 0.2 to 0.8 wt %, the hydrolysis rate decreases by 3–5 times. Cooling of the components leads to the increase in hydrolysis time and the decrease in the maximum temperature. Silica particles were found in the xerogel structure against the background of the matrix. Their size and number depends on the nitric acid amount and was found to be 0.5–10 μm. The highest number of particles was observed when using cooled components and HNO₃ amount was 0.8 wt %.

To obtain a hydrolysate with a low gelation rate, the amount of concentrated HNO₃ in the system should be

in the range of 0.4–0.6 wt % with pre-cooling of the initial components.

References

- [1] Sajjadi S.: J. Polym. Eng. Technol., 2015, **13**, 38. <http://polymer.aut.ac.ir/>
- [2] Lutsyuk I., Vakhula Ya.: Chem. Chem. Technol., 2018, **12**, 386. <https://doi.org/10.23939/chcht12.03.386>
- [3] Bertolini M., Zaghete M., Gimenes R., Paiva-Santos C.: Mater. Lett., 2005, **59**, 3196. <https://doi.org/10.1016/j.matlet.2005.04.054>
- [4] Skrozniukova V., Popovich N., Dimitrov Ts.: Nauchni Trudove na Rusenska Universitet, 2013, **52**, 61.
- [5] Vakhula Ya., Vasijchuk V., Romaniv A., Semchuk O.: Chem. Chem. Technol., 2007, **1**, 103.
- [6] Maeda H., Nakano Y., Kasuga T.: J. Nanomater., 2013, **2013**, 1064. <https://doi.org/10.1155/2013/463048>
- [7] Adams L., Essien E., Shaibu R., Oki A.: New J. Glass Ceram., 2013, **3**, 11. <https://doi.org/10.4236/njgc.2013.31003>
- [8] Skorodumova O., Tarakhno O., Goncharenko D., Shuba I.: Keramichni Kompozytsyini Materialy i Vognestiiki Pokrytiana Osnovi Hybrydnykh Geliv. FOPPanova, Kharkiv 2017.
- [9] Semchenko G.: Zol-Gel Process v Keramicheskoi Technologii. Kharkov 1997.

Received: January 12, 2021 / Revised: April 13, 2021 / Accepted: February 02, 2021

КАТАЛІТИЧНА ДІЯ НІТРАТНОЇ КИСЛОТИ НА ГІДРОЛІЗ ЕТИЛСІЛКАТУ ЕТС-40

Анотація. Досліджено вплив концентрованої нітратної кислоти на швидкість гідролізу етилсілікату ЕТС-40. Визначено тривалість і максимальну температуру гідролізу етилсілікату за різної температури компонентів. Показано утворення кремнеземистих частинок в структурі ксерогелю. Вивчено вплив особливостей проведення гідролізу ЕТС-40 на розмір і концентрацію частинок. Структуру ксерогелю та склад утворених частинок досліджено за допомогою електронно-мікроскопічного (СЕМ) та енергодисперсійного аналізів (EDX).

Ключові слова: етилсілікат ЕТС-40, гідроліз, ксерогель, кремнеземисті частинки.